

ISSN: 0976-3031

Available Online at <http://www.recentscientific.com>

CODEN: IJRSFP (USA)

International Journal of Recent Scientific Research
Vol. 15, Issue, 04, pp.4658-4664, April, 2024

**International Journal of
Recent Scientific
Research**

DOI: 10.24327/IJRSR

Research Article

EXPERIMENTAL STUDY ON MECHANICAL PROPERTIES OF MACRO SYNTHETICS FIBERS-REINFORCED BINARY CONCRETE MADE BY GROUND GRANULATED BLASTFURNACE SLAG AND FLY ASH

M. Venkata Maheswara Reddy ^{1*} and S. Krishnaiah²

^{1,*} Research scholar and ²Professor,

Department of Civil Engineering, Jawaharlal Nehru Technological University, Anantapur (JNTUA),
Anantapuram - 515002, Andhra Pradesh, India

DOI: <http://dx.doi.org/10.24327/ijrsr.20241504.0871>

ARTICLE INFO

Article History:

Received 20th February, 2023

Received in revised form 19th March, 2023

Accepted 17th April, 2024

Published online 28th April, 2024

Keywords:

Macro synthetic fibers, Fly ash, Ground-granulated blast furnace slag, Mechanical properties, Supplementary cementitious material, Fiber reinforced concrete, Binary concrete.

ABSTRACT

Concrete production involves using vast quantities of ordinary portland cement (OPC), the primary binder material. However, OPC production uses high embodied energy and emits more CO₂ into the atmosphere. One of the alternatives is using industrial waste or by products such as fly ash (FA) and ground granulated blast furnace slag (GGBS) as supplementary cementitious material. However, the main drawbacks of conventional concrete with or without supplementary cementitious material are its brittleness and lower elasticity. This led to the addition of fibers to concrete. The current experimental study's objective is to ascertain concrete's mechanical properties before using it for pavements. The proportions of supplementary cementitious materials (SCM) such as ground granulated blast furnace slag (GGBS), fly ash (FA) and macro synthetic fiber (MSF) were tuned to assess the properties of M40 grade fiber-reinforced concrete. In this study, the effects of macro synthetic fibers (MSF), 20% FA class F, and 20%, 25%, 30%, 35%, and 40% GGBS were used as supplementary cementitious materials to produce MSF-reinforced binary concrete of grade 40 MPa. MSF of aspect ratio 36 was added to the mix at various percentages: 0%, 0.5%, 1%, 1.5%, and 2% by volume fraction. The results showed that the MSF fiber-reinforced binary concrete workability decreased with an increase in the addition of MSF. Mechanical Properties such as compressive strength, split tensile strength and flexural strength for fiber-reinforced binary concrete mix with the addition of 1.5% MSF, replacement of 20% FA and 30% GGBS of cement content yield satisfactory results compared to the control mix. Incorporating MSF, GGBS, and FA reduces OPC usage, enhances strength characteristics, and contributes to cost reduction in construction.

Copyright© The author(s) 2024, This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution and reproduction in any medium, provided the original work is properly cited.

INTRODUCTION

Concrete plays a crucial global significance as a construction material. The booming infrastructure and progress have resulted in a surge in construction activities, thus driving up the need for ordinary Portland Cement (OPC). In order to fulfil the demand for OPC, there has been significant production growth. However, this has resulted in a substantial depletion of resources for the cement industry and a global emission of 5–7% of CO₂ [1]. The maximum strength of regular OPC relies on the creation of C-S-H gel through the cement hydration

process [2]. Therefore, in modern technology, different materials have been chosen to achieve the necessary durability of concrete, substituting cement. Conversely, growing industrialization has resulted in a significant quantity of industrial waste being produced. These waste materials need significant quantities of area for disposal or various treatment procedures to be effectively utilized. Therefore, including these waste products in the concrete production process while considering their properties can effectively decrease the

*Corresponding author: **M. Venkata Maheswara Reddy**

Department of Civil Engineering, Jawaharlal Nehru Technological University, Anantapur (JNTUA),
Anantapuram - 515002, Andhra Pradesh, India

environmental impact, waste management expenses, and concrete manufacturing costs [3-6]. Similarly, practitioners and researchers are working to improve and modify the characteristics of concrete. As evidenced by research studies [7,8], there is a trend in the field to experiment with natural, manufactured, or designed fibers as well as different kinds of waste materials to improve the qualities of concrete.

The current study incorporates waste materials from the iron industry and thermal power plants, commonly referred to as ground-granulated blast furnace slag (GGBS) and fly ash (FA) [9-12], respectively, into the concrete mixture. The cementitious properties of these wastes rely on their specific surface area and the pozzolanic behaviour of their mineral composition. On a global scale, it is estimated that the yearly production of FA falls within the range of 0.75 to 1 billion tons [13]. Similarly, the production of GGBS typically ranges from 300–540 kg per ton, or rough iron used for mineral feed, with an iron content of 60–65%. In steel production, around 150–200 kg of GGBS are produced per ton of liquid steel. As developing nations have a growing demand for affordable energy, it is expected that this production volume will increase in the future [14]. Therefore, the widespread use of these wastes can be accomplished through their application in civil engineering [15].

As stated above, concrete has high compressive strength but low tensile strength [16-17]. Therefore, in order to examine the impact of fibers in conjunction with GGBS and FA, the researchers chose to incorporate polypropylene fibers (0–2.5% of the cement's weight) as an additive during the concrete preparation process [18]. It serves as an auxiliary material for reinforcing concrete. Incorporating fibers into concrete can prevent the development of shrinkage cracks and improve its mechanical characteristics [19-20]. Therefore, the authors decided to include engineered fibers (0.5% by weight of cement) as an addition in manufacturing concrete to investigate the effects of fibers in conjunction with GGBS and PVC waste powder. Engineered fibers are polypropylene fibers that have been altered. It is used to mix concrete as a supplementary reinforcing ingredient. Adding fibers to concrete will stop shrinkage cracks from forming and improve its mechanical qualities. Recron 3s fibers may be added to the concrete at a weight percentage of 0.2% to 1.5% used in previous studies [19,21]. Research such as [22,23] suggests that GGBS can replace cement to between 30 and 50%. However, the authors of this study decided to adjust the percentage of PVC waste powder, 0.5% designed fiber, and 0.6% superplasticizer in addition to fixing GGBS at 30%. Generally, the gravimetric or weight analysis approach is used for solid goods, and the volumetric analysis approach is usually used for liquid or semi-liquid things. The authors of this study adhered to the Indian standard IS: 10262-2019 [24], which provides explicit instructions for weight or gravimetric analysis for mix proportioning and calculation. Aggregates, such as cement, are considered by weight when determining general material mix proportions. Conversely, according to Indian standards, concrete is measured by volume (1 m³). Qiana et al. [25] have investigated the improvement of fly debris, fiber size, and content in a composite material made of equal parts polypropylene and steel fibers mixed with concrete. The amount of fiber used in the mixture was modest, but it still had a significant impact on the overall mechanical properties of the material. The researchers discovered that the use of steel strands of different sizes resulted in varying mechanical

properties, albeit to varying extents. Furthermore, it was observed that the choice of a tiny fiber type had an impact on the compressive strength, whereas the flexural strength was slightly affected. The presence of a large fiber type leads to opposite mechanical effects, which are further intensified by increasing the aspect ratio. Sivakumar et al. [26] evaluated the mechanical characteristics of several solid structures reinforced with fibers, including steel strands alone and combinations of steel with non-metallic filaments such as glass, polyester, and polypropylene. The filaments were maintained at a fixed absolute dosage of 0.5%. Based on the results, the researchers found that only the polypropylene fiber blend (containing 0.12% polypropylene filaments) outperformed the mono-steel fiber concrete in all aspects. It was observed that the flexural strength decreased as the amount of non-metallic strands increased.

Research Significance and Objective

There is a lack of research on the utilization of MSF in binary blended concrete, specifically in combination with GGBS and FA. Therefore, the objective of the present study is

- To investigate the physical and mechanical characteristics of binary concrete by incorporating macro synthetic fibers (MSF) in combination with GGBS and FA.
- To determine the properties of concrete when OPC is partially substituted with GGBS at varying percentages 20%, 25%, 30%, 35%, 40% and with constant 20% FA. In addition, several volume fractions of MSF (0.5%, 1%, 1.5% and 2%) were incorporated into the concrete.
- To compare the findings with standard M40 grade concrete to assess the impact of incorporating MSF, GGBS, and FA on the concrete's properties [12].

MATERIALS

Ordinary Portland cement (OPC)

OPC 53 grade (Indian Standard Code : IS: 269-2015) [27,28], with a specific gravity of 3.14 was used in this investigation. The initial setting time of the OPC was 65 minutes, whereas the final setting time was 220 minutes. The Blain's specific surface area was measured to be 295 m²/kg, and the soundness was 0.6 mm.

Ground-granulated blast furnace slag (GGBS) and fly ash (FA)

GGBS (Indian Standard Code: IS 16714:2018) [29] and FA (Indian Standard Code IS 3812: 2013) [30] with a specific gravity of 2.86 and 2.17, respectively. The Blains specific surface area of GGBS was 388 m²/kg was used in this work. The study utilized JSW brand GGBS and Ramagundam thermal power plant-based FA. Table 1 displays the chemical makeup of cement, GGBS, and FA. Fig. 1 displays SEM pictures showing that the FA particles mostly have a spherical shape, but the GGBS particles have more irregular crystals.

Aggregates

Crushed stone aggregate with a maximum diameter of 20mm, a specific gravity of 2.64, a bulk density of 1.68 kg/litre, and a water absorption of 0.26% was utilized. As per the specifications of Indian Standard code i.e IS 383-2016 [31], Zone-II river sand was utilized as a fine aggregate, possessing a specific gravity of 2.58 and a bulk density of 1.82 kg/liter.

Table 1 Chemical composition of OPC, GGBS and FA

Constituent (wt.%)	OPC	GGBS	FA
SiO ₂	23.4	37.73	60.2
CaO	60.76	37.34	15.98
Al ₂ O ₃	5.01	14.42	22.3
MgO	3.95	8.71	1.15
Fe ₂ O ₃	4.46	1.8	0.17
SO ₃	2.42	-	0.2

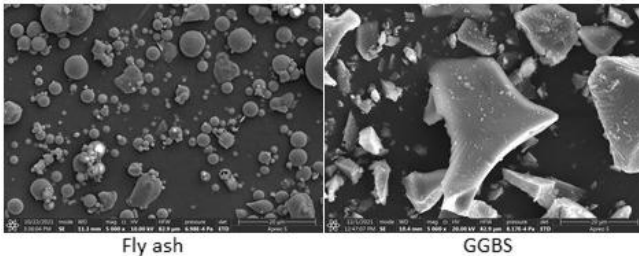


Fig.1.SEM pictures of FA and GGBS

Superplasticizer

The superplasticizer used in this study was Master Glenium Sky 8609 (Indian Standard Code :IS 9103) [32], which was procured from M/s. Master Builders Solutions India Pvt. Ltd.

Macro Synthetic Fibers (MSF)

The MSF are designed to meet the specifications of ASTM C1116 Type III, ensuring their outstanding performance. Table 2 depicts the properties of MSF.

Table 2 Properties of MSF

Properties	Value
Density	0.910 g/cm ³
Diameter	0.8-1.8 mm
Length	45-50 mm
Tensile strength	>500 Mpa
Modulus of Elasticity	>= 7000 Mpa
Aspect Ratio	36

EXPERIMENT METHODOLOGY

The concrete mix design was formulated as per Indian Standard Code IS 10262-2019 [33]. The mix design maintains a constant binder content of 450 kg/m³ and a water-binder ratio of 0.36. The volume of aggregates for design concrete was obtained by assuming that 1.5% of entrapped air is present in the fresh concrete. The aggregate volume per cubic meter of concrete determines the weight of the aggregates. For this study, different combinations were devised to assess the compressive strength, split tensile strength, and flexural strength of concrete, both with and without fibers. Table 3 displays the proportions of the concrete mixture and the designations of the mixture.

The specimens were cured under water at 27 ± 2 °C until the appropriate age was obtained after casting. Standard code provisions were then used to evaluate concrete specimen characteristics at 7 and 28 days. Following IS 1199, a 300 mm high cone frustum serves as the mould for the concrete slump test. The base measures 200 mm in diameter, with a smaller hole measuring 100 mm at the top. The foundation is set atop a level surface, and the container is filled with three layers of concrete, the durability of which will be examined. Using a

standard steel rod with a rounded end, each layer is tempered 25 times. Using the tamping rod's screening and rolling motion, the concrete-filled mould's top surface is struck off or levelled with the mould top opening. Using handles or footrests brazed to the mould, the mould can be securely held against its base throughout the process to prevent it from moving as the concrete is poured. The cone is cautiously and slowly raised vertically when the filling is finished and the concrete is levelled; unsupported concrete will sag. A slump is a reduction in the height of the slumped concrete's centre. The slump is assessed by positioning the cone next to the depressed concrete and then covering it with the tamping rod to extend over the slumped concrete. The scale shows how the concrete's height decreases compared to the mould's. (typically expressed as to the nearest 5 mm). Compressive strength was tested on 150mm concrete cubes in a 300-ton compression testing machine at 14 N/mm²/minute until failure, according to Indian Standard Code IS: 516 [35]. A 150 mm cube specimen was placed between the compression testing machine's platens and loaded at 1.2–2.4 N/mm²/minute until failure for tensile strength, as described in Indian Standard Code IS: 516 [34]. A 100 mm X 100 mm X 500 mm prism was placed on a 40-ton Universal Testing Machine (UTM) to assess flexural strength. The specimen was then gradually loaded with four points, as indicated in Indian Standard Code IS: 516 and Indian Standard Code IS: 17161 [35,36].

RESULTS AND DISCUSSION

Workability

Slump cone test results for various MSF-reinforced binary concrete mixes are shown in Fig. 2. As the MSF content increases, the slump values gradually decrease. The slump values are higher for the conventional mix than for all other samples. Even though the slump values decrease due to adding MSF to concrete mixes, all samples are in an excellent workable stage per IS standards. It is clear from Fig. 2 that SP5 shows a higher slump of 125mm and SP29 shows a lower slump of 45mm. Generally, all fiber types (i.e., steel, micro and macro synthetic) in the concrete mix can "ball up." This may occur if insufficient fine particles are in the mixture to which the fibers are introduced. The likelihood of the fibers balling reduces when they are glued and covered in fines. When introduced to the mix at a consistent, uniform rate (ribbon-fed), Artificial fibers have the potential to "ball". The results show no balling effect of MSF in binary concrete, and fibres are dispersed uniformly. An increase in the percentage of MSF content decreases concrete workability due to increased MSF stiffness compared to the reference mix.

Compressive Strength

The results of the compressive strength of MSF-reinforced binary concrete are presented in Fig. 3. As the age of concrete increases, the compressive strength also increases due to continuous hydration. Because of the hydration process, cement concrete gains compressive strength over time. The chemical process called hydration occurs when cement and water are combined. This reaction creates new crystalline compounds, such as CSH gel. The cement paste's strength increases due to the CSH gel's ongoing development and interlocking this process can go on for a long time and gradually raise compressive strength. The addition of MSF resulted in a slight enhancement of the compressive strength of the binary concrete.

Table 3 Mix Proportions (kg/m³)

Mix ID	W/C (ratio)	Cement (kg/m ³)	Macro synthetic fibres (MSF) %	Cementitious material (kg/m ³)		Fine Aggregate (kg/m ³)	Coarse Aggregate (kg/m ³)	Admixture (kg/m ³)
				GGBS	FA			
SP0	0.36	450	0.0	0.0	0.0	758.40	1026.80	0.90
SP1	0.36	450	0.5	0.0	0.0	758.40	1026.80	0.90
SP2	0.36	450	1.0	0.0	0.0	758.40	1026.80	0.90
SP3	0.36	450	1.5	0.0	0.0	758.40	1026.80	0.90
SP4	0.36	450	2.0	0.0	0.0	758.40	1026.80	0.90
SP5	0.36	270	0.0	90	90	758.40	1026.80	0.90
SP6	0.36	248	0.0	112	90	758.40	1026.80	0.90
SP7	0.36	225	0.0	135	90	758.40	1026.80	0.90
SP8	0.36	203	0.0	157	90	758.40	1026.80	0.90
SP9	0.36	180	0.0	180	90	758.40	1026.80	0.90
SP10	0.36	270	0.5	90	90	758.40	1026.80	0.90
SP11	0.36	248	0.5	112	90	758.40	1026.80	0.90
SP12	0.36	225	0.5	135	90	758.40	1026.80	0.90
SP13	0.36	203	0.5	157	90	758.40	1026.80	0.90
SP14	0.36	180	0.5	180	90	758.40	1026.80	0.90
SP15	0.36	270	1.0	90	90	758.40	1026.80	0.90
SP16	0.36	248	1.0	112	90	758.40	1026.80	0.90
SP17	0.36	225	1.0	135	90	758.40	1026.80	0.90
SP18	0.36	203	1.0	157	90	758.40	1026.80	0.90
SP19	0.36	180	1.0	180	90	758.40	1026.80	0.90
SP20	0.36	270	1.5	90	90	758.40	1026.80	0.90
SP21	0.36	248	1.5	112	90	758.40	1026.80	0.90
SP22	0.36	225	1.5	135	90	758.40	1026.80	0.90
SP23	0.36	203	1.5	157	90	758.40	1026.80	0.90
SP24	0.36	180	1.5	180	90	758.40	1026.80	0.90
SP25	0.36	270	2.0	90	90	758.40	1026.80	0.90
SP26	0.36	248	2.0	112	90	758.40	1026.80	0.90
SP27	0.36	225	2.0	135	90	758.40	1026.80	0.90
SP28	0.36	203	2.0	157	90	758.40	1026.80	0.90
SP29	0.36	180	2.0	180	90	758.40	1026.80	0.90

The compressive strength of SP22 is observed to be higher than that of other samples at all ages.

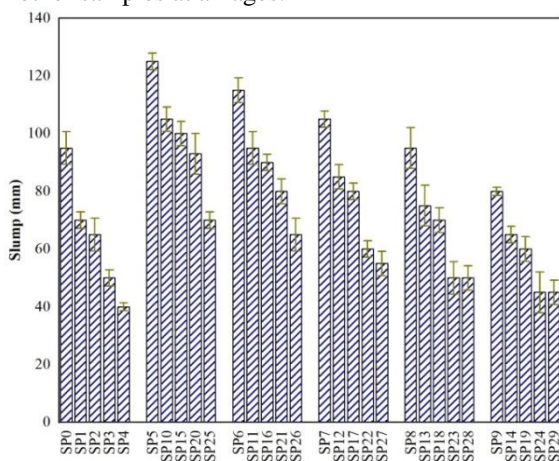


Fig.2 Workability of MSF-reinforced binary concrete mixes

The compressive strength of mix SP22 improved by 9.84% and 5.8%, respectively, compared to mix SP0 at 7 and 28 days. The improvement in the strength of the binary concrete was more pronounced after 28 days of curing. The continuous hydration process led to stronger bonding between the MSF and supplementary cementitious materials (i.e., GGBS and FA),

achieving higher strength. As MSF is used, the bonding between the MSF and supplemental cementitious materials is powerful, contributing to strength improvement. MSF enhanced the OPC matrix's structural integrity, delaying the cracks' beginning, growth, and spread. This significantly increased post-cracking load resistance and improved compressive strength [18].

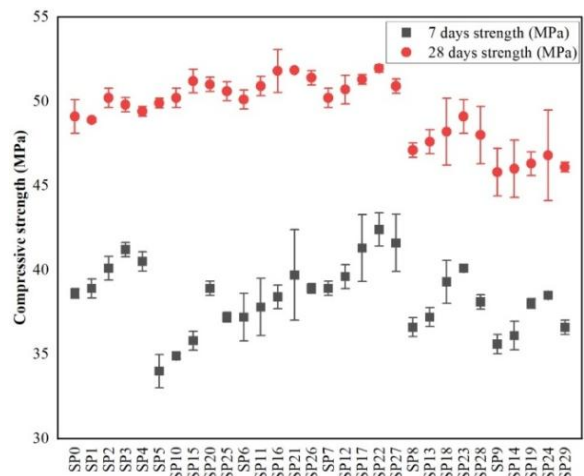


Fig.3 Compressive strength of MSF-reinforced binary concrete mixes

Split tensile strength

The findings of the splitting tensile strength of MSF-reinforced binary concrete are presented in Fig. 4. The split tensile strength increased by incorporating MSF content ranging from 0.5 to 2% into the binary concrete, improving tensile strength. The split tensile strength of SP22 is observed to be higher than that of SP0 at 7 and 28 days, respectively. At 7 days, the tensile strength of mix SP22 was higher by 65.18% compared to mix SP0. Similarly, at 28 days, the tensile strength of mix SP22 was superior by 61.31% compared to SP0. The increase in split tensile strength with the addition of MSF to the binary concrete is due to the high tensile strength of the fibre, which invariably increases the tensile strength of all the samples. The MSF also made the concrete more flexible and resistant to load after cracking by stopping cracks from starting, growing, and spreading when it was under tensile load, which increased its tensile strength [19,37].

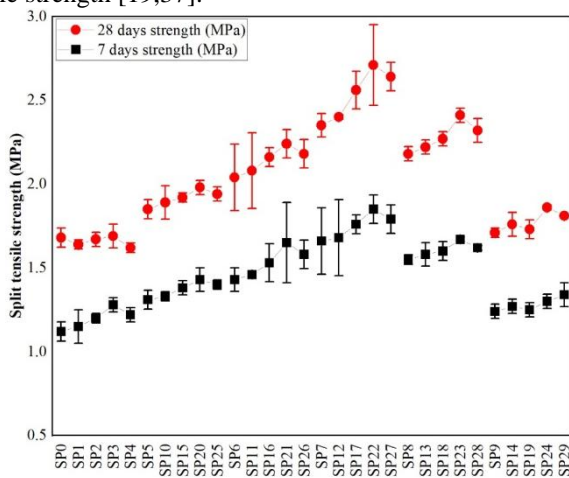


Fig.4 Split tensile strength of MSF-reinforced binary concrete mixes

Flexural strength

The results of the MSF-reinforced binary concrete are presented in Fig. 5.

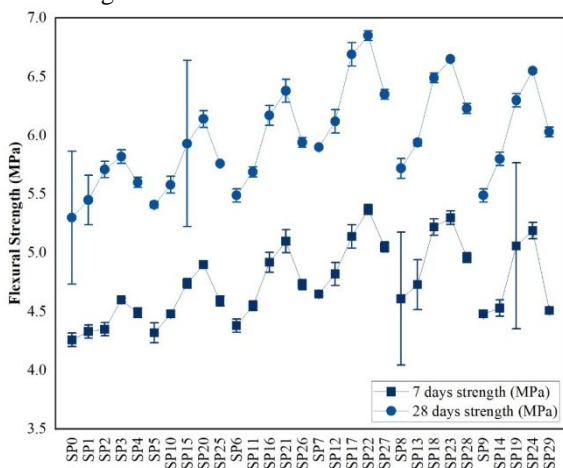


Fig.5. Flexural strength of MSF-reinforced binary concrete mixes

When the compressive and tensile strengths increased, the binary concrete's flexural strength rose when the MSF content increased on each of the corresponding days. Compared to the SP0, the flexural strength of mixed SP22 mixes was higher by 20.65% at 7 days and 26.22% at 28 days, respectively. The addition of MSF is mostly responsible for the increase in flexural strength. Additionally, the high tensile strength of

MSF (>500 MPa) significantly improved the bending resistance of binary concrete when added to the mix. Furthermore, due to its crack bridging through strong bonding, MSF increases the resistance to post-cracking failure and delays the failure of the concrete when it is subjected to bending loads by transferring and redistributing stresses throughout the matrix [26,38]

CONCLUSIONS

In this study, the impact of MSF in various percentages (0%, 0.5%, 1%, 1.5%, and 2%) on the use of GGBS in varying percentages (20%, 25%, 30%, 35%, and 40%) with 20% FA is attempted.

- This research shows the workability of MSF-reinforced binary concrete compared to reference mix SP0. Similarly, the same workability improvement trend is noticed for the SP5 sample with a slump of 125mm prepared with 20% FA and 20% GGBS. It indicates that using ultrafine particles of FA and GGBS improves the fluidity properties of MSF-reinforced binary concrete and lessens the internal friction between supplementary cementitious materials. Similarly, using a higher amount of MSF decreases the workability of concrete.
- Compressive strength results indicate that GGBS can be used up to 30% along with FA (20%) without affecting the strength characteristics of MSF-reinforced binary concrete. After that, a marginal decrease in compressive strength is noticed for the mixes using 2% MSF. Cao and Al₂O₃ in GGBS and FA waste powder, respectively, react with cement constituents and form CSH gel formation, thus improving concrete properties over time. Similarly, using MSF (1.5% by volume) in MSF-reinforced binary concrete reduces the voids, arrests the micro-crack formation, and makes mixes less porous. Thus, improvement in strength is noticed until mixed (1.5% MSF, 20% FA and 30% GGBS), with a 28-day strength of more than 51 Mpa, justifying MSF.
- A tensile strength improvement of 2.71 MPa is noticed for sample SP22 (1.5% MSF, 20% FA and 30% GGBS) compared to a strength of 1.68 MPa for SP0. However, using 2% MSF affects the strength. This improvement in strength established the role of MSF, resulting in a dense concrete microstructure and reduced voids and crack formation.
- Like compressive and tensile strength, a comparable trend was observed, with a flexural strength improvement of 6.85 MPa for sample SP22 (1.5% MSF, 20% FA, and 30% GGBS) compared to a strength of 5.30 MPa for SP0. However, using 2% MSF affects the strength. MSF usage slows the growth of microcracks both before and after peak stress, and the iron concentration of GGBS increases the density of the concrete.

Limitations of the study and scope for future work

The study illustrates using MSF and partially replacing OPC with GGBS and FA without compromising the strength qualities, which is in keeping with the goal and scope of this research. This study examined the effects of fibres in GGBS and FA on the mechanical and fresh characteristics of M40-

grade concrete. Other concrete grades and other additive and superplasticizer combinations were not covered.

While these experiments aid in the development of new green concrete by academics and practitioners, much more work has to be done to understand the usage of MSF in different percentages in different grades of concrete. Similarly, by employing mathematical or optimization or modelling, the researchers may expand their study to ascertain the best use of GGBS, FA, and MSF. The authors hope this study will pave the way for further investigations and applications that benefit practitioners and scholars.

Acknowledgement

The authors express their deep gratitude to Prof. V. Vinayaka Ram Department of Civil Engineering, BITS- Pilani Hyderabad Campus for his valuable support in conducting this research. Also, the authors are grateful to JNTUA Anantapuram and M/s STEDRANT Technoclinic Pvt Ltd, Hyderabad for providing testing facilities and valuable support in conducting this research.

References

1. J. Prasara-A, S Fig.5. Flexural strength of MSF-reinforced binary concrete mixes. H. Gheewala, Sustainable utilization of rice husk ash from power plants: A review, *J. Clean. Prod.* 167 (2017) 1020–1028. <https://doi.org/10.1016/j.jclepro.2016.11.042>.
2. B. Lu, C. Shi, G. Hou, Strength and microstructure of CO₂ cured low-calcium clinker, *Constr. Build. Mater.* 188 (2018) 417–423. <https://doi.org/10.1016/j.conbuildmat.2018.08.13>.
3. M.I. Khan, M.A.A. Sayyed, M.M.A. Ali, Examination of cement concrete containing micro silica and sugarcane bagasse ash subjected to sulphate and chloride attack, *Mater. Today Proc.* 39 (2020) 558–562. <https://doi.org/10.1016/j.matpr.2020.08.468>.
4. I. Khan, B. Challa, S. Haripriya Varma, M.A.A. Sayyed, Sorptivity and durability assessment of dolomite impregnated ternary concrete, *Int. J. Recent Technol. Eng.* 8 (2019) 5676–5681. <https://doi.org/10.35940/ijrte.B2896.078219>.
5. I. Khan, M. Sravanthi, E.L. Prasanna, An experimental study of the mechanical properties of a glass fiber reinforced high strength concrete partially replacing cement with nano silica, *Int. J. Civ. Eng. Technol.* 9 (2018) 1398–1409. <https://doi.org/10.34218/IJCIET.09.4.2018.155>
6. S. Haripriya, B. Rajesh, D.S. Sudarshan, M.I. Khan, B. Bhaskar, Strength Characteristics of Recycled Aggregate Concrete by Ann, *Int. J. Innov. Technol. Explor. Eng.* 9 (2020) 1210–1214. <https://doi.org/10.35940/ijitee.c8624.019320>.
7. M.D.I. Khan, M.A. Abdy Sayyed, G.S. Yadav, S.H. Varma, The impact of fly ash and structural fiber on the mechanical properties of concrete, *Mater. Today Proc.* 39 (2021) 508–512. <https://doi.org/https://doi.org/10.1016/j.matpr.2020.08.242>.
8. O. Ragab, A. Ahmed, A. Hassab El Nabi, K. Hashim, O. El Shazly, O. El Sherbini, S. Khedr, M. Abdel Mooty, M. Saady, O. El Kadi, Development of bendable concrete and rigid pavement overlay application, *Proceedings, Annu. Conf. - Can. Soc. Civ. Eng.* 2019-June (2019).

9. A.A.J. Ghanim, F.U. Rahman, W. Adil, A.M. Zeyad, H.M. Magbool, Experimental investigation of industrial wastes in concrete: Mechanical and microstructural evaluation of pumice powder and Fly Ash in concrete, *Case Stud. Constr. Mater.* 18 (2023) e01999. <https://doi.org/10.1016/j.cscm.2023.e01999>.
10. G.O. Bamigboye, D.E. Basse, D.O. Olukanni, B.U. Ngene, D. Adegoke, A.O. Odetoyan, M.A. Kareem, D.O. Enabulele, A.T. Nworgu, Waste materials in highway applications: An overview on generation and utilization implications on sustainability, *J. Clean. Prod.* 283 (2021) 124581. <https://doi.org/10.1016/j.jclepro.2020.124581>.
11. S.H. Helmy, A.M. Tahwia, M.G. Mahdy, M.A. Elrahman, Development and characterization of sustainable concrete incorporating a high volume of industrial waste materials, *Constr. Build. Mater.* 365(2023)130160. <https://doi.org/10.1016/j.conbuildmat.2022.130160>.
12. M.I. Khan, V.V. Ram, V.I. Patel, Influence of Pretreatment Methods for Coarse Recycled Aggregates on the Performance of Alkali-Activated Concrete, *Arab. J. Sci. Eng.* (2023). <https://doi.org/10.1007/s13369-023-08436-x>.
13. A. Dindi, D.V. Quang, L.F. Vega, E. Nashef, M.R.M. Abu-Zahra, Applications of fly ash for CO₂ capture, utilization, and storage, *J. CO₂ Util.* 29(2019)82–102. <https://doi.org/10.1016/j.jcou.2018.11.011>.
14. U.S.R. Krishna, C.N.S. Kumar, A study on concrete mix with quaternary blended sustainable materials for ultra-thin white topping, *Jordan J. Civ. Eng.* 14 (2020) 161–170.
15. I.B.O.F. MINES, Indian Minerals Yearbook 2016, Gov. India Minist. Mines Nagpur. 13 (2018) 1–17.
16. V. Venkata Krishna Bhargava, K.J. Brahma Chari, V. Ranga Rao, Experimental investigation of M40 grade concrete with supplementary cementitious materials and glass fiber, *Mater. Today Proc.* 33 (2020) 519–523. <https://doi.org/10.1016/j.matpr.2020.05.209>.
17. A.G. Toroslu, An Experimental Study on the Properties of Recycled High-Density Polyethylene, *Int. Polym. Process.* 36(2021) 557–563. <https://doi.org/10.1515/ipp-2020-4071>.
18. M.D. Ikramullah Khan, M.A. Abdy Sayyed, G. Swamy Yadav, S. Haripriya Varma, The impact of fly ash and structural fiber on the mechanical properties of concrete, *Mater. Today Proc.* 39 (2020) 508–512. <https://doi.org/10.1016/j.matpr.2020.08.242>.
19. T. Simões, H. Costa, D. Dias-da-Costa, E. Júlio, Influence of type and dosage of micro-fibres on the physical properties of fibre reinforced mortar matrixes, *Constr. Build. Mater.* 187 (2018) 1277–1285. <https://doi.org/10.1016/j.conbuildmat.2018.08.058>.
20. R.P. Manfredi, F. de Andrade Silva, Test Methods for the Characterization of Polypropylene Fiber Reinforced Concrete: A Comparative Analysis, *KSCE J. Civ. Eng.* 24 (2020) 856–866. <https://doi.org/10.1007/s12205-020-0741-7>.
21. R.P. Nanda, A.K. Mohapatra, B. Behera, Influence of metakaolin and Recron 3s fiber on mechanical properties of fly ash replaced concrete, *Constr. Build. Mater.* 263 (2020) 120949. <https://doi.org/10.1016/j.conbuildmat.2020.120949>.
22. V.B.R. Suda, P.S. Rao, Experimental investigation on

- optimum usage of Micro silica and GGBS for the strength characteristics of concrete, *Mater.Today Proc.* 27(2020)805811. <https://doi.org/10.1016/j.matpr.2019.12.354>.
23. S.V.B. Reddy, P. Srinivasa Rao, Experimental studies on mechanical properties and impact characteristics of ternary concrete with steel fiber, *Mater. Today Proc.* 27 (2020) 788–797. <https://doi.org/10.1016/j.matpr.2019.12.344>.
 24. I.S:10262, Indian standard, Concrete mix Proportioning – Guidelines (Second Revision)., *Bis.* (2019) 1–42.
 25. C.X. Qian, P. Stroeven, Development of hybrid polypropylene-steel fibre-reinforced concrete, *Cem. Concr. Res.* 30 (2000) 63–69. [https://doi.org/10.1016/S0008-8846\(99\)00202](https://doi.org/10.1016/S0008-8846(99)00202)
 26. A. Sivakumar, M. Santhanam, Mechanical properties of high strength concrete reinforced with metallic and non-metallic fibres, *Cem. Concr. Compos.* 29 (2007) 603–608.
 27. IS 269, Requirements of Ordinary Portland Cement, *Bur. Indian Stand.* New Delhi, India. (2015).
 28. M. Bhawan, B. Shah, Z. Marg, Product Manual For Ordinary Portland Cement According TO IS 269 : 2015 List of Test Equipment, (2018) 1–14.
 29. IS-16714, Indian Standard Ground Granulated Blast Furnace Slag for Use in Cement, Mortar and Concrete- Code of Practice, (2018).
 30. I. 3812 (Part1): 2013, specification Pulverized Fuel Ash - Specification: Part 1 For Use as Pozzolana in Cement, Cement Mortar and Concrete, *Bur. Indian Stand.* New Delhi, India. (2013) 1–12.
 31. IS:383, Indian Standard Coarse and Fine aggregate for Concrete- Specification, *Bur. Indian Stand.* New Delhi. (2016) 1–21.
 32. IS 9103 : 2020, Product Manual for Concrete Admixtures, *Bur. Indian Stand.* New Delhi. (2020) 1–9.
 33. IS 10262:2019, Concrete Mix Proportioning- Guidelines, in: *Bur. Indian Stand.*, 2019 pp.1–40.
 34. IS:516 Part-1/Sec-1, Hardened concrete - Methods of test, *Bur. Indian Stand.* IS 516-2021, New Delhi, India. 54 (2021) 1–20. www.standardsbis.in.
 35. I. Standard, Indian Standard, Flexural Strength and Toughness Parameters of Fibre Reinforced Concrete- Method of Test, *Bur. Indian Stand.* (2020). www.standardsbis.in.
 36. IS:516 Part-5/Sec-4, Hardened concrete - Methods of test, *Bur. Indian Stand.* IS 516-2021, New Delhi, India. 54 (2021) 1–20. www.standardsbis.in.
 37. A.M. Alhozaimy, P. Soroushian, F. Mirza, Mechanical properties of polypropylene fiber reinforced concrete and the effects of pozzolanic materials, *Cem. Concr. Compos.* 18(1996)8592. [https://doi.org/10.1016/09589465\(95\)00003-8](https://doi.org/10.1016/09589465(95)00003-8).
 38. J.N. Jha, A.K. Choudhary, K.S. Gill, S.K. Shukla, Behavior of plastic waste fiber-reinforced industrial wastes in pavement applications, *Int. J. Geotech. Eng.* 8 (2014) 277–286. <https://doi.org/10.1179/1939787914Y.0000000044>.

How to cite this article:

M. Venkata Maheswara Reddy and S. Krishnaiah. (2024). Experimental study on mechanical properties of macro synthetics fibers-reinforced binary concrete made by ground granulated blastfurnace slag and fly ash. *Int J Recent Sci Res.* 15(04), pp.4658-4664.
